

Spin dynamics and magnetic correlation length in two-dimensional quantum Heisenberg antiferromagnets

P.Carretta¹, T.Ciabattoni¹, A.Cuccoli², E.Mognaschi¹, A.Rigamonti¹, V.Tognetti², and P.Verrucchi².

¹ *Dipartimento di Fisica "A. Volta" and Unità INFM di Pavia, Via Bassi, 6 I-27100 Pavia, Italy.*

² *Dipartimento di Fisica dell'Università di Firenze and Unità INFM di Firenze, Largo E. Fermi, 2 I-50125 Firenze, Italy.*
(February 1, 2008)

The correlated spin dynamics and the temperature dependence of the correlation length $\xi(T)$ in two-dimensional quantum ($S = 1/2$) Heisenberg antiferromagnets (2DQHAF) on square lattice are discussed in the light of experimental results of proton spin lattice relaxation in copper formate tetradeuterate (CFTD). In this compound the exchange constant is much smaller than the one in recently studied 2DQHAF, such as La_2CuO_4 and $\text{Sr}_2\text{CuO}_2\text{Cl}_2$. Thus the spin dynamics can be probed in detail over a wider temperature range. The NMR relaxation rates turn out in excellent agreement with a theoretical mode-coupling calculation. The deduced temperature behavior of $\xi(T)$ is in agreement with high-temperature expansions, quantum Monte Carlo simulations and the pure quantum self-consistent harmonic approximation. Contrary to the predictions of the theories based on the Non-Linear σ Model, no evidence of crossover between different quantum regimes is observed.

In recent years, it has been argued that the pairing mechanism leading to high-temperature superconductivity can occur in the presence of quantum critical fluctuations, as the ones expected in two-dimensional quantum ($S = 1/2$) Heisenberg antiferromagnets (2DQHAF) [1,2]. This early observation has triggered a novel interest on the correlated spin dynamics in 2DQHAF. Several studies have been carried out on the behavior of the magnetic correlation length ξ as a function of temperature and/or disorder, and on the possibility of driving quantum phase transitions by hole doping. In particular, for a given degree of disorder (i.e. doping) the temperature is expected to cause the transition to a regime with peculiar quantum spin excitations, which could be responsible for novel pairing mechanisms [3]. In spite of an enormous amount of experimental and theoretical efforts this issue is still controversial [4,5]. Thus, it is believed that it is necessary first to unravel the problem of the spin dynamics and of the temperature dependence of $\xi(T)$ in pure 2DQHAF.

The 2DQHAF with nearest-neighbor interaction on square lattice, is described by the Hamiltonian

$$\mathcal{H} = \frac{J}{2} \sum_{\mathbf{j}, \mathbf{a}} \mathbf{S}_{\mathbf{j}} \cdot \mathbf{S}_{\mathbf{j}+\mathbf{a}}, \quad (1)$$

with $J > 0$ and $\mathbf{a} = (0, \pm a), (\pm a, 0)$, a being the lattice constant. The 2DQHAF has been commonly described in terms of the 2-dimensional Quantum Non-Linear σ Model (QNL σ M) [6], with the action given by

$$S = \frac{1}{2g} \int_{-\infty}^{\infty} \int_0^u d\mathbf{x} d\tau (|\nabla \mathbf{n}|^2 - |\partial_\tau \mathbf{n}|^2); \quad |\mathbf{n}|^2 = 1, \quad (2)$$

where $\mathbf{n}(\mathbf{x})$ is a unitary 3D vector field, $g = c_s \Lambda / \rho_s$ and $u = c_s \Lambda / T$ are the coupling and the imaginary-time cut-off respectively. This mapping is rigorous only in the

large-spin limit, where ρ_s and c_s are the spin stiffness and the spin-wave velocity of the correspondent magnetic model. This approach can be extended to $S = 1/2$ provided that c_s and ρ_s are introduced as fitting parameters. Then a rich and interesting phase diagram can be devised [2,7,8]. Accordingly, the QNL σ M has arisen to a great popularity, both for basic quantum magnetism studies as well as a good candidate to describe the modifications in the microscopic properties of a 2DQHAF when it becomes a high- T_c superconductor upon charge doping.

One of the most striking predictions is the presence of the so called *quantum criticality*, in a well defined temperature window. Below a finite value of g , by increasing the temperature, the system should cross from the *renormalized classical* to the *quantum critical* regime and eventually to the classical behavior [2,8].

It was suggested that this scenario could be probed by studying the temperature behavior of the static correlation length $\xi(T)$. The latter can be directly estimated by neutron scattering [9–11] or by the longitudinal NMR relaxation rate, which provides an indirect measure of ξ [12,13]. While for small ξ ($\simeq a$), neutron scattering studies become difficult and accuracy problems arise, it has been proved [12] that NMR relaxation, driven by the correlated spin dynamics, can be a suitable tool to derive the temperature and doping dependence of the magnetic correlation length.

The behavior of ξ , according to the QNL σ M approach, considerably changes in the various regimes [2,8,9]. Until now, most of the discussion on the correlation length in 2DQHAF with $S = 1/2$ has dealt with La_2CuO_4 and $\text{Sr}_2\text{CuO}_2\text{Cl}_2$. However, in these compounds the large value of $J \sim 1500 K$ prevents one to obtain experimental results above $T/J \sim 0.6$ and thus a detailed comparison with the theoretical predictions is difficult. As a mat-

ter of fact the region where the quantum critical regime is expected, according to the QNL σ M approach, should be $0.4 < T/J < 0.8$. Neutron scattering experiments in antiferromagnets with larger S have been recently carried out with good accuracy [10,11] and no evidence of crossover has been found in a large range of T/J . Indeed these data are in agreement with high-temperature expansion (HTE) results [14], quantum Monte Carlo (QMC) data [15] and with the results of the pure quantum self-consistent harmonic approximation (PQSCHA) recently obtained by some of us [16,17]. The latter approach is reliable for any realistic temperature range for $S \geq 1$, and it gives good results starting from $T/J \gtrsim 0.35$ for $S = 1/2$ [17].

The advantage of CFTD is that besides being a good prototype of $S = 1/2$ 2DQHAF on the square lattice (the interlayer interaction constant is less than $10^{-4}J$), still J is rather small ($J \sim 80 K$) so that the experiments can be carried out in a wide range of T/J . Thus the classical behavior is approached and a comprehensive analysis becomes possible. In particular, one can explore also the temperature range where the correlation length is of the same order of the lattice constants a . ^1H NMR experiments have been performed on a $5 \times 5 \times 4 \text{ mm}^3$ single crystal of copper formate tetradeuterate ($\text{Cu}(\text{HCO}_2)_2 \cdot 4\text{D}_2\text{O}$) [18]. The spin-lattice relaxation rate $1/T_1$ has been measured in a 8 kGauss magnetic field ($g\mu_B H \ll J$) applied perpendicular to the ab plane, by using standard pulse sequences. In Fig.1 the experimental data for $1/T_1$ are reported.

The relaxation rates can be calculated, through the mode-coupling (MC) approach [19–21]. First, we calculate the normalized Kubo relaxation function [22]:

$$F_{\mathbf{k}}(t) = \frac{R_{\mathbf{k}}(t)}{R_{\mathbf{k}}(0)}, \quad R_{\mathbf{k}}(t) = \int_0^{1/T} \langle S_{\mathbf{k}}^\alpha(t + i\lambda) S_{\mathbf{k}}^\alpha \rangle d\lambda, \quad (3)$$

by solving the following integro-differential equation [19–21]:

$$\frac{d}{dt} F_{\mathbf{q}}(t) = -\frac{2}{N} \sum_{\mathbf{k}} (J_{\mathbf{k}} - J_{\mathbf{q}-\mathbf{k}}) (J_{\mathbf{k}} - J_{\mathbf{q}}) \times \frac{T}{\lambda + J_{\mathbf{k}}} \int_0^t F_{\mathbf{k}}(t-t') F_{\mathbf{q}-\mathbf{k}}(t-t') F_{\mathbf{q}}(t'), \quad (4)$$

where $J_{\mathbf{k}} = J \sum_{\mathbf{a}} \exp(\mathbf{k} \cdot \mathbf{a})$, and λ is a temperature-dependent parameter which fixes the static susceptibility of the system and can be directly related to $\xi(T)$ [21].

By means of the spectral theorem the dynamic cross section $\mathcal{S}_{\mathbf{k}}(\omega)$ can be obtained from the Fourier transform of $F_{\mathbf{k}}(t)$. Thus the longitudinal relaxation time is given by [23]:

$$1/T_1 = \frac{\gamma^2}{2N} \sum_{\mathbf{k}} \mathcal{S}_{\mathbf{k}}(\omega) [A^2 + B^2(\cos(k_x a) + \cos(k_y b))], \quad (5)$$

where $\gamma = 2\pi \cdot 42.576 \cdot 10^2 \text{ s}^{-1} \text{ Gauss}^{-1}$. The form factors $[A^2 + B^2(\cos(k_x a) + \cos(k_y b))]$ have been derived by assuming the hyperfine coupling of ^1H nuclei with the two Cu^{2+} nearest neighbors only. The coupling constants have been estimated from the rotation pattern by rotating the crystal around the a -axis in a field of 94 kGauss. In this way the transferred hyperfine interaction constant was directly obtained. The dominant dipolar part was determined through lattice sums (details will be published elsewhere [24]). The two coupling constants turned out $A = 2.31 \text{ kGauss}$ and $B = 1.46 \text{ kGauss}$.

The analysis in terms of the theoretical models requires the knowledge of the exchange constant J . *Ad-hoc* neutron and light scattering experiments, leading to the best estimate of J , have been performed in La_2CuO_4 [25]. Analogous methods to evaluate J in CFTD are under way [26]. At the moment in CFTD we can assume a value around $J = 80 K$. Estimates based on the velocity of the spin waves [27] are in the same range, as well as old data [28] (within 10%), in agreement with the dispersion curve determined by neutron scattering near the zone-boundary [26].

The MC scheme requires the static quantities as an external input. For this purpose the simplest and self-consistent approach is to use those pertaining to the two-dimensional spherical model [21]. An alternative method is to rely on the results obtained for $\xi(T)$ by the PQSCHA to determine the parameter λ appearing in Eq. (4), for $T/J \gtrsim 0.35$. The two theoretical curves are reported in Fig.1. Furthermore we have used the more precise QMC data for $\xi(T)$ [15] to calculate the relaxation rate at lower temperatures, down to the value of $T \simeq 20 K$, where three dimensional ordering effects are revealed by the NMR experimental findings. The relaxation rate $1/T_1$ should be weakly temperature dependent in the quantum critical regime [8], without any observable minimum around $T/J = 0.5$ ($T = 40 K$). Instead the experimental data do present such a minimum, which is completely reproduced by our approach. Moreover, in a wide temperature range the behavior of $\xi(T)$ is also consistent with the renormalized classical regime [29]. The minimum in $1/T_1$ is related to the $\mathbf{k}$ dependence of the hyperfine form factor in Eq. (5), which is strongly peaked at the center of the BZ but non zero at the AF wave-vector $\mathbf{k} = (\pi/a, \pi/a)$. One has to notice that in the temperature range far from the transition the spherical model seems to be a good approximation, as shown also by the temperature-dependence of the correlation length in Fig.2.

The remarkable agreement between MC calculations and the experimental results, allows us to derive the cor-

relation length $\xi(T)$ from the experimental data through an *inversion* of the mode-coupling approach. The results are shown in Fig.2 together with the theoretical predictions. The success of the mode-coupling approach gives further support to the validity of the scaling hypothesis, and the correlation length can be extracted with satisfactory accuracy from the relaxation rate, by means of a procedure which has already yielded reliable quantitative estimates in La_2CuO_4 (see Refs. [12,13] for details). Indeed, when $\xi(T) \gg a$ classical scaling arguments for the generalized susceptibility and the decay constants lead to the following equation [12]:

$$1/T_1 = \gamma^2 \epsilon \frac{S(S+1)}{3} \left(\frac{\xi}{a}\right)^{z+2} \frac{\beta^2 \sqrt{2\pi}}{\omega_e} \left(\frac{a^2}{4\pi^2}\right) \times \int_{\text{BZ}} d\mathbf{q} \frac{[A^2 + B^2(\cos(q_x a - \pi) + \cos(q_y a - \pi))]}{(1 + q^2 \xi^2)^2} \quad (6)$$

thus establishing a one-to-one correspondence between $1/T_1$ and $\xi(T)$. In Eq. (6) the 2-d wavevector $\mathbf{q}$ starts from the BZ boundary $(\pi/a, \pi/a)$, corresponding to the AF ordering wavevector; ω_e is the Heisenberg exchange frequency describing the fluctuations in the limit of infinite temperature, $z = 1$ the dynamical scaling exponent, $\epsilon = 0.33$ takes into account the reduction of the amplitude due to quantum fluctuations [30] and β is a normalization factor preserving the sum rule for the amplitude of the collective modes. Also the data for $\xi(T)$ obtained by means of this procedure are reported in Fig. 2. It is apparent that the values for $\xi(T)$ are close to the ones deduced by mode-coupling approach, the main differences being at low values of ξ , as expected.

From the comparison with the theoretical estimates, the permanence of the system in the renormalized classical regime, on moving towards the classical one at highest temperatures, is shown. No evidence of crossover to the quantum critical regime appears, as is clearly shown in the inset of Fig.2. Finally we point out that although we used a value of $J = 80 \text{ K}$ in all our calculations, the main conclusions derived regarding the absence of a crossover towards a quantum critical regime do not depend on J .

Summarizing, we have used a single crystal of a proper 2DQHAF which allows one to analyze the behavior of the in-plane correlation length $\xi(T)$ over a wide temperature range in the light of several theoretical models. $\xi(T)$ has been derived from ^1H NMR relaxation rates, having verified also that the mode-coupling theory is able to reproduce successfully the temperature dependence of $1/T_1$. It turns out that $\xi(T)$ is well described by QMC, PQSCHA and HTE. In particular, at variance with other recent theories for 2DQHAF, no crossover to the quantum critical regime occurs, up to temperatures $T/J \simeq 1.5$, where the classical behavior has already set on. Finally, Eq. 6, which is based on the validity of the scaling hypothesis, is shown to yield reliable estimates of $1/T_1$ even for $\xi \simeq a$.

The authors would like to acknowledge the scientific


correspondence and discussions with H.M. Rønnow and D.F. McMorrow. We thank also R.Vaia for discussions and R.Birgeneau and Y.S. Lee for exchange of information.

-
- [1] A. Sokol and D. Pines, Phys. Rev. Lett. **71**, 2813, (1993).
 - [2] S. Chakravarty, B.I. Halperin and D.R. Nelson, Phys. Rev. B **39**, 2344, (1989).
 - [3] see D. Pines, Z. Phys. B **103**, 129 (1997) and references therein
 - [4] M.S. Makivic and H.Q. Ding, Phys. Rev. B **43**, 3562, (1991); J.-K. Kim, D.P. Landau and M. Troyer, Phys. Rev. Lett. **79**, 1583 (1997).
 - [5] B.B.Beard et al., Phys. Rev. Lett. **80**, 1742 (1998)
 - [6] F.D.M. Haldane, Phys. Rev. Lett. **50**, 1153, (1983).
 - [7] P. Hasenfratz and F. Niedermayer, Phys. Lett. B **268**, 231, (1991).
 - [8] A.V. Chubukov, S. Sachdev and J. Ye, Phys. Rev. B **49**, 11919, (1994).
 - [9] M. Greven *et al.*, Z. Phys. B **96**, 465, (1995).
 - [10] Y.S. Lee *et al.*, Eur. Phys. J. B **5**, 15 (1998). S. Fulton, R.A. Cowley, A. Desert, and T. Mason, J. Phys. Cond. Matt. **6**, 6667 (1994).
 - [11] R.L. Leheny, R.J. Christianson, R.J. Birgeneau, and R.W. Erwin, Phys. Rev. Lett. **82**, 418 (1999). R.J. Birgeneau *et al.* preprint (1999)
 - [12] P. Carretta, A. Rigamonti and R. Sala, Phys. Rev. B **55**, 3734, (1997).
 - [13] T. Imai et al., Phys. Rev. Lett. **70**, 1002 (1993).
 - [14] N. Elstner *et al.*, Phys. Rev. Lett. **75**, 938, (1995).
 - [15] K. Harada, M. Troyer and N. Kawashima, J. Phys. Soc. Jpn. **67**, 1130 (1998).
 - [16] See, for example, A. Cuccoli, R. Giachetti, V. Tognetti, R. Vaia, P. Verrucchi, J. Phys.: Condens. Matter **7**, 7891 (1995) and reference therein.
 - [17] A. Cuccoli, V. Tognetti, R. Vaia and P. Verrucchi, Phys. Rev. B **56**, (1997).
 - [18] K. Okada et al., J. Chem. Phys. **44**, 1648 (1966); N. Burger and H. Fuess, Ferroelectrics **22**, 847 (1979)
 - [19] J. Hubbard, J. Phys. C **4**, 53 (1971).
 - [20] K. Kawasaki in *Phase Transitions and Critical Phenomena*, ed. C. Domb and M.S. Green, vol. 5a (Academic, London, 1976)
 - [21] A. Cuccoli, S.W. Lovesey and V. Tognetti, Phys. Rev. B **39**, 2619 (1989); S.W. Lovesey, E. Engdhal, A. Cuccoli and V. Tognetti, J. Phys. CM **6**, 7099 (1994). A mode coupling approach for the relaxation time in La_2CuO_4 has been performed by T. Nagao and J. Igarashi, J. Phys. Soc. J. **67**, 1029 (1998).
 - [22] S.W. Lovesey *Condensed Matter Physics: Dynamic Correlations, Frontiers in Physics* (Benjamin, New York, 1986).
 - [23] A. Rigamonti, F. Borsa and P. Carretta, Rep. Prog. Phys. **61**, 1367 (1998).

- [24] P. Carretta, T. Ciabattini and E. Mognaschi, in preparation
- [25] S.M. Hayden, G. Aeppli, R. Osborn, A.D. Taylor, T.G. Perring, S-W. Cheong and Z. Fisk; Phys. Rev. Lett. **67**, 3622, 1991.
- [26] H.M. Rønnow, Private Communication.
- [27] S.J. Clarke *et al* J. Phys. Cond. Matt., **4**, L71 (1992)
- [28] K. Yamagata, Y. Kozuka and T. Morita, J. Phys. Soc. Jpn, **50**, 421, (1981)
- [29] It should be mentioned that although our data for $S_{\mathbf{k}}(\omega)$ in La_2CuO_4 coincide with the ones derived by Nagao *et al.* (see Ref. 21), we find a discrepancy by a factor 2 (*at all temperatures*) in the estimate of $1/T_1$, when the same form factor is used. The origin of this discrepancy is unclear, but it does not affect our main conclusion in favour of a temperature dependence of $1/T_1$ well described by the mode-coupling theory (see Fig. 1).
- [30] P. Bourges, H. Casalta, A.S. Ivanov and D. Petitgrand, Phys. Rev. Lett. **79**, 4906 (1997).

FIG. 1. Proton spin-lattice relaxation $1/T_1$ as a function of temperature. Squares: experimental data; dashed-line: theoretical mode-coupling (MC) results using the static quantities of the spherical model; full line: MC results using the correlation length given by the PQSCHA for $T/J > 0.35$; filled circles: MC results using the correlation length given by QMC simulations for $T/J < 0.35$ [4].

FIG. 2. Correlation length ξ vs temperature. Squares: experimental data deduced from $1/T_1$ by inversion of Eq. (6); circles: experimental data deduced from $1/T_1$ by inversion of mode-coupling results leaving λ as a free parameter; dashed-line: spherical model; full line: PQSCHA; triangles: QMC simulations [4]. In the inset we report the corresponding data for $\xi(T)$ derived from Eq. (6) and from the spherical model as a function of the inverse temperature. According to the predictions of the QNL σ M the QCR should occur for $0.4 < T/J < 0.8$ (i.e. $0.016 \lesssim 1/T \lesssim 0.036$), with a correspondent linear behavior of $\xi(T)$ vs. $1/T$, at variance with the experimental findings.

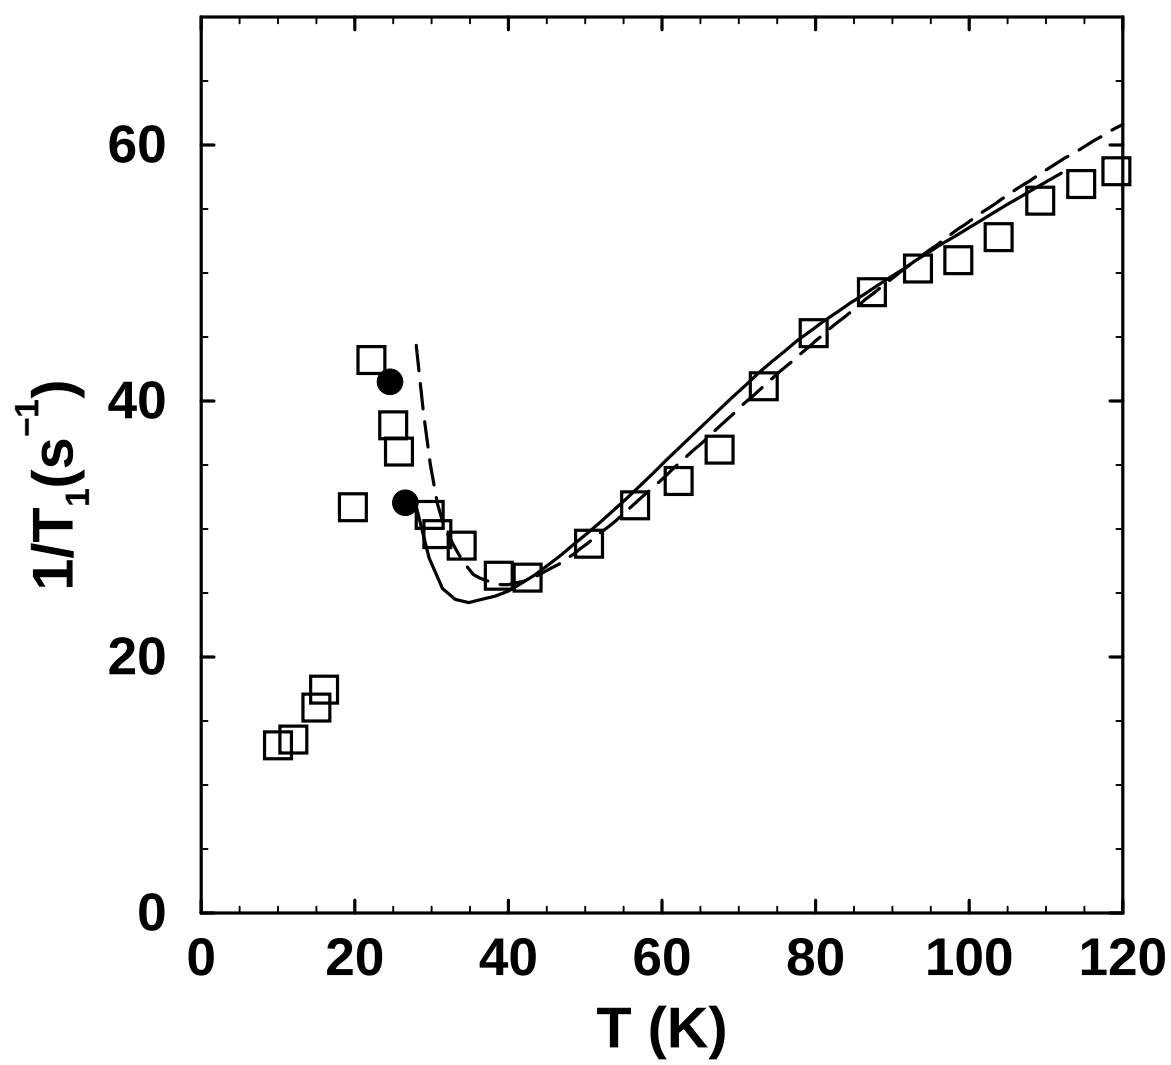

T (K)

0 20 40 60 80 100 120

